

CrossRef DOI of original article:

1 Optimization of Turning Parameters using RSM During Turning 2 of AISI H11 with Dimple Textured Uncoated Carbide Tool

3

4 *Received: 1 January 1970 Accepted: 1 January 1970 Published: 1 January 1970*

5

6 **Abstract**

8 **Index terms—**

9 **1 INTRODUCTION**

10 Developments in the metal cutting industry are driven by the manufacturer's need to expand the performance of
11 parts used for various applications by maintaining the environmental legislation.

12 Extreme heat develops at cutting edge while machining "difficult-to-cut" materials, which is carried out by
13 workpiece, tool, and coolant/lubricants. Traditionally, to dissipate heat large quantity of coolants (flooded
14 coolants) is used to minimize friction and heat, which create difficulties in procurement, dumping, storage, and
15 preservation. However, some disadvantages like cost, environmental impact, safety, and health hazards limit the
16 use of flood cooling which compels industries to minimize or eliminate its use and encourage the development of
17 new cooling/lubricating options. "Dry machining" is oldest, most environmentally friendly options, but absence
18 of cutting fluid leads to heat generation, adhesion, poor chip evacuation, and increase friction at the cutting zone.
19 Dry machining is found to lead to poor results with rough surface on products, whereas flood cooling leads to
20 economic, environmental, and health challenges.

21 Worldwide manufacturers are actively seeking cost-effective alternatives to produce satisfactory quality
22 components which are accepted globally.

23 To promote the metal cutting industry and creating new opportunities, technology plays an important role.
24 Turning at one time is based on the skills of the operator and still important, so to be competitive it is necessary
25 to adopt and implement modern and cost-efficient manufacturing techniques (Soroka, 2003).

26 Materials used extensively in aerospace, food, and the nuclear industry have great-strength and wear-resistance
27 are "difficult-to-machine" due to thermo-physical stresses at the edge of cutting tool (Sharma, Dogra and Suri,
28 2008). The degradation of the surface finish is closely associated with wear growth. Different researchers working
29 on enhancing tool life during conventional turning; otherwise, tool failure refers to the damage that is so severe
30 to remove material from the workpiece due to its vulnerability to changes in cutting conditions (Sharma, Dogra
31 and Suri, 2009). Tool-workpiece friction and heat generation at cutting area are prevalent challenges in turning,
32 reducing life of tool and compromising the quality of surface during turning operation.

33 Due to unusual properties of "difficult-to-machine" materials, such as low conductivity to heat, great-strength
34 at eminent temperatures, and wear-resistance and corrosion generate heat and produce negative effects (Zhang,
35 Li and Wang, 2012). Enormous generation of heat (indicated in Fig. ??1) at the cutting zone while turning
36 "difficult-to-cut" materials, is due to plastic deformation because of chip formation and friction between the
37 tool-work-piece and tool-chip. Dissipation of heat is dependent on geometry of tool, its heat conductivity, and
38 cooling techniques (Shokrani, Dhokia and Newman, 2012). Surface topography moderation of cutting tools using
39 textures has been an innovative/ecological method, which helps to improve tribological conditions of sliding
40 surfaces relative to each other, and the addition of solid lubricant in the pockets generated on the tool makes dry
41 machining environmental friendly (Sharma and Pandey, 2016).

42 Dry machining with surface texturing tends to be the most suitable solution for sustainable machining. But
43 for hard materials, high-temperature gradient at cutting zone necessitates the use of traditional flood cooling,
44 which makes the process harmful for ecological considerations (Mosarof et al., 2016).

45 **2 Dry Machining**

46 Dry machining is an eco-friendly approach and it will be mandatory for the industries in the coming future to
47 enforce regulations of environment sustainability for occupational safety and health standards (Klocke, F., &
48 Eisenblätter, 1997).

49 Dry turning/machining offers pollution-free atmosphere (or water); no swarf residues that are measured by
50 decreased disposal and cleaning costs; no health hazards; no skin and allergy (Sreejith and Ngoi, 2000). Dry
51 machining helps to create an environmentally friendly image, reduce costs, and improve work satisfaction in
52 workers (Figure ??2). The major issues during dry machining include overheating, enhanced abrasion, diffusion
53 and oxidation of the tool material. However, a significant amount of heat inhibits near tolerances and its surface
54 is subjected to metallurgical damage (Debnath, Reddy and Yi, 2014).

55 **3 London Journal of Engineering Research**

56 Dry hard turning of difficult-to-machine materials would not be feasible without the selection of appropriate tool
57 material. Costly, CBN (cubic boron nitride) tools are widely applied to machine high hardness and thermal
58 conductivity materials, since these are second toughest tool material after diamond. Various merits or demerits
59 of dry hard turning are discussed in Table ??1. The cost of the CBN tool is high, but tool wear is low in
60 comparison to other tool materials (Kundrák et al., 2006). Cemented carbide tools have been developed over
61 time and still to be primarily used to machine Ni-alloys, particularly Inconel-718.

62 Conversely, with the increase demand for high MRR and higher surface quality, machining at high speed was
63 adopted and usage of cemented carbide tools became more complex (Dudzinski et al., 2004). For dry turning of
64 Inconel-718, cutting tool material must meet the following requirements (Dudzinski et al., 2004):

65 **4 Textures Engraved on Tool Surface**

66 "Surface structuring or surface texturing on the cutting tool is an innovative strategy for sustainable metal
67 cutting. Surface texturing is a term that refers to the process of altering the topography of a surface to enhance
68 tribological efficiency of contact surfaces" (Fatima and Mativenga, 2013; Ghosh and Rao, 2015). In the last decade,
69 textures on surface has been the feasible option in surface engineering, leading to considerable increments in load
70 carrying capacity, wear, strength, friction coefficient, etc. of tribo-mechanical components (Etsion, 2005). The
71 surface texture reduces the friction coefficient, cutting forces and sticking between the tool-chip interface (Jianxin
72 et al., 2012). Different researchers have graved various textures for this reason on tool inserts (Ghosh and Rao,
73 2015).

74 Metal cutting processes are now carried out at high speeds to ensure optimum efficiency, thanks to the
75 advancement of modern engineering technologies. In the era of automation, long continuous chips produced
76 at high cutting rates have become a challenge for industry. Textures on tool surface helps to control contact
77 because their length of contact is shorter than conventional contact length of chip (Chao and Trigger, 1959).

78 Surface textures are generated by a variety of advanced manufacturing techniques, which include; micro-
79 wire cut "electron discharge machining" (EDM), "Focused ion beam" (FIB) machining (Tseng, 2004), and
80 photolithography, "reactive ion etching" method (RIE), laser technology, and so forth (Pettersson and Jacobson,
81 2003). Texture geometries such as micro-holes, linear, circular, square, and wavy indentations, were developed
82 on tool surfaces and its application improves the cutting tool tribological performance (Etsion, 2005).

83 **5 II. LITERATURE**

84 Nowadays, the tendency is toward high-quality, cheap, and small-batch sizes. To compete with countries
85 having structure of low-wage in manufacturing industry, it is vital to innovate techniques that contribute to
86 the improvement of the manufacturing sector's level, with a beginning to witness technical improvements in
87 the field of hard turning (Soroka, 2003). Generally, when the hardness of material is more than 45 HRC, then
88 it is called hard turning ??Pavel et When texture surface chip-tool friction is reduced and the wear debris
89 that forms from this is confined in the cavity owing to textures on the surface (Blatter et al., 1999; Costa and
90 Hutchings, 2009). During the turning of materials hard to machine, a comparative examination of textured and
91 conventional cutting tools was done. Textured tools utilized in the turning process, helps to reduce friction,
92 heat generation, and thus wear, which helps to improve energy efficiency, product quality, and tool life (Ling et
93 al., 2013) The textures orientation at the cutting edge has been demonstrated to increase or decrease cutting
94 performance, several studies have examined this in terms of sliding contacts. The tribological performance of
95 parallel direction, perpendicular direction, and at a 45°angle to the sliding direction was tested (Pettersson and
96 Jacobson, 2004); and found that orientation modification helps pressure accumulation due to textures; which
97 disrupt surface roughness.

98 It is observed that perpendicular texture displayed more extraordinary film thickness under higher loads,
99 whereas narrower parallel grooves exhibited a flow-direction because the lubricant may be directed away from
100 contact in a parallel groove and so reduces the thickness of the film and tribology (Costa and Hutchings, 2007).
101 The angle of textures was essential since they alter the lubricant's capacity to capture wear particles (Zhan and
102 Yang, 2012). The foregoing tests show that textures must be oriented towards the sliding direction since it has a
103 direct effect on the texture mechanism which promotes the tribological performance on a contact surfaces. For

104 the building grooves in parallel on the rake tool face (known as textured tool), EDM has been used (Kim et
105 al., 2015) and evaluated its influence on the cuts in comparison with conventional tool. Some researchers have
106 discriminate textures (Fig. ??,1, showing perpendicular shape, parallel shape, and cross patterns) to chip flow
107 direction using femtosecond laser on WC inserts (Kawasegi et al., 2009). Wear resistance of tool is found to
108 increased greatly in comparison to conventional insert while machining carbon steel with four kinds of textured
109 tool because this micro-grooved surface collects the wear particles created by wear mechanisms (Enomoto and
110 Sugihara, 2010).

111 Four varieties (perpendicular, parallel, square-shaped pits and dots) as depicted in Fig. ??,2 were produced
112 in the same way. Micro-scale textures in orthogonal and diagonal sites showing that using rake and flank face
113 grooves decreases tool wear as compared with ordinary tools (Xie et al., 2012). Diagonal micro-sites reduce
114 wear of tool by 6.7% and increase heat dissipation rate in the cutting are due to texture orientation to the chip
115 flow direction. Uncoated cemented carbide tool with texture on the rake face is utilized in comparison to costly
116 CBN tools for turning "difficult-to-machine" materials. The tool holder (WTJNR1616H16) and cutting insert
117 on clamping, gave approach angle (93°), clearance angle (6°), rake angle (-6°) and nose radius (0.80 mm). The
118 dimensions of tool holder (in mm) are given in Table ??,4.

119 6 III. EXPERIMENTAL SETUP

120 7 Fabrication of Surface Texture on Rake Face (Dimple Shape)

121 In general, the several "micro-machining" techniques for removing materials, such as 'micro-grinding', 'micro-
122 EDM', 'femtosecond laser' and 'fibre laser' have been used.

123 Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated
124 Carbide Tool

125 Dimple-shaped texture with 50 μm diameter and 100 μm special distance, as illustrated in Fig. ??,1 a,b, is
126 taken into consideration and is modelled using CAD software. The CAD model was then exported to appropriate
127 interface for fabricating texture on tool rake surface. A "multidiode pump fibre laser" (LM-487-A-22-SD6-UX-
128 M30-M) was applied on uncoated carbide tool's rake surface, the array of dimple texture is taken zigzag and the
129 direction parallel to cutting edge was fabricated.

130 The conventional insert with non-textured and dimple-textured pictures was measured by optical microscope
131 and is displayed in Fig. ??,1 a, b.

132 8 Machine and Measuring Equipment

133 The turning runs were conducted on convention lathe HMT, India, model: high-speed precision lathe NH 22 and
134 for tool flank wear and surface roughness measurement Metzer toolmaker's microscope Surf Test SJ-201 analyzer
135 are utilized.

136 To measure the cutting forces during cutting a strain gauge based digital lathe dynamometer supplied by RMS
137 controls, India was used during experimentation. The specifications of cutting force dynamometer is given in
138 Table ??,5. "Scanning electron microscopy" was used to characterize the wear of worn-out cutting inserts.

139 The SEM/EDAX equipment is shown in Figure ??,6 with the following specifications, associated with two
140 computer interface for wear and elemental analysis, respectively.

141 9 London Journal of Engineering Research

142 Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated
143 Carbide Tool 37

144 10 IV. MODELING OF FLANK WEAR AND SURFACE 145 ROUGHNESS

146 To generate models for response factors, i.e., tool flank wear and surface roughness, an entire set of 20 experiments
147 obtained through RSM based on CCFC (central composite face-centered) design have been conducted. The input
148 turning parameters viz. cutting speed, feed rate, and depth of cut were varied over 3 levels, whereas the tool
149 geometry and texture on the rake surface were kept constant for each experiment. The new cutting edge of the
150 insert was used to conduct each turning test. CCFC experimental layout, along with results obtained for output
151 responses, i.e., tool flank wear (VB) and surface roughness (Ra), is shown in Table 4.1.

152 In order to build their respective models in terms of input factors, the output responses were examined using
153 RSM. The quadratic model was presented the best fit for both output factors, whereas cubic models had been
154 aliased, in Table 4.2 and Table 4.3.

155 The recommended quadratic models' R-Squared (R^2) values were the greatest (except the aliased one), while
156 their associated PRESS values remain lowest, indicating quadratic model's superiority over other source models.

157 Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated
158 Carbide Tool Likewise, R^2 or R-squared = 1-(residual sum of squares / total sum of squares) was higher than
159 0.85, for both models, which confirmed furthermore the accuracy of the models that were fitted with regard to

160 the projection of capability of response parameters. The values of output responses that are predicted by the
161 adjusted R² and R² indicate excellent interactions. In addition, adequate precision (AP: signal/noise ratio) >
162 4, shows the validity of the models for future predictions for both models. Furthermore, the lowest press values
163 (predicted residuals error sum of squares): 0.2568 and 0.2107, shows quadratic models for output responses are
164 best fit models for the test findings. To create a connection between response variables and input turning factors,
165 multiple regression analysis was used to produce output response (VB and Ra) mathematical models. Table 4.8
166 lists empirical models for output responses. To check the accuracy of developed models for VB and Ra, shown
167 in Table ??, the values of VB and Ra have been calculated from these regression equations for a different
168 combination of input parameters, as reported in Table 4. Fig. 4.3 reported high wear at flan with higher feed
169 rate/ speed. Initially, the tool edge was protected by hard particle and rake face textures, which limits chip
170 tool contact, resulting in less tool flank wear, as the speed and feed rate rises, temperature between tool-chip
171 interfaces becomes dominating factor. At high speed cutting, the friction rises due to uneven contact with a
172 chip-tool, which causes the protective layer to be removed, i.e. adhesive wear. Furthermore, due to the high
173 temperature during cutting, the bonds between tool particles are weakened by the severe diffusion between the
174 work material and tool. The hard particles are thus removed from the tool and wear is thereby enhanced. The
175 tool flank wear (VB) rises with an increase in feed rate, but above the mean value, the VB increases quickly. A
176 reduction in tool flank wear was seen with a combination of low cutting speed and low feed. to the effects of
177 feed rate, as, at lower speed of cutting, Ra is higher, and as the speed increases, up to 130 m/min. values of Ra
178 decreases. But with the further increment of speed of cutting does not have a noteworthy effect on Ra.

179 Whereas on other hand, the cuts depth (d) has a significant influence on roughness (Ra). At lower depth of
180 cut (0.2 mm), surface roughness is nearly 2.23 μm , while with rise in cuts depth, roughness increases up to 2.98
181 μm . As illustrated in Fig. 4.7, the lowest roughness of surface was achieved by low depth of cut and speed of
182 cutting.

183 For optimizing turning variables for AISI H11 multi-response optimization using desirability function was
184 employed with uncoated carbide tool to achieve minimal tool flank wear (VB) and surface roughness (Ra) using
185 textured tools. The numerical optimization algorithm seeks a set of factors levels that simultaneously satisfies
186 the criteria placed on each response factor with highest combined desirability. The various constraints applied
187 throughout the optimization process are described in Table 4.9. The cutting parameters were determined to be
188 optimal as: cutting speed ($V_c = 86.61 \text{ m/min.}$), feed rate ($f = 0.16 \text{ mm/rev.}$) and depth of cut ($d = 0.2 \text{ mm}$)
189 with projected optimum value of $VB = 1.82 \mu\text{m}$ and $Ra = 1.79 \mu\text{m}$ at a desirability level of 0.967 (Table 4.10;
Solution no.1).




11

Figure 1: Figure 1 . 1 :





Figure 3:

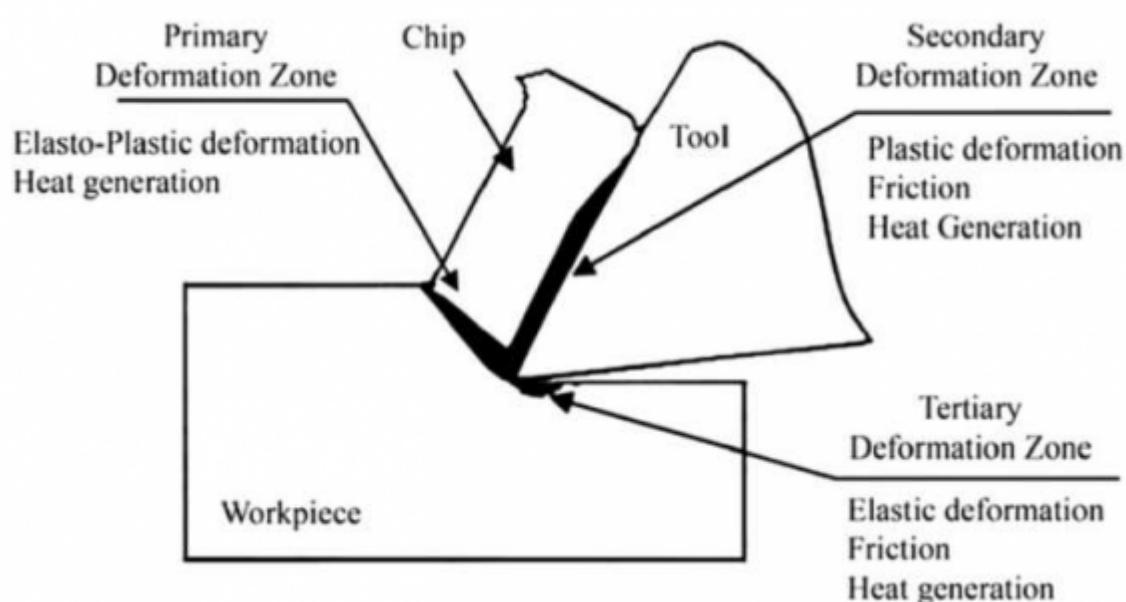

21


Figure 4: Figure 2 . 1 :

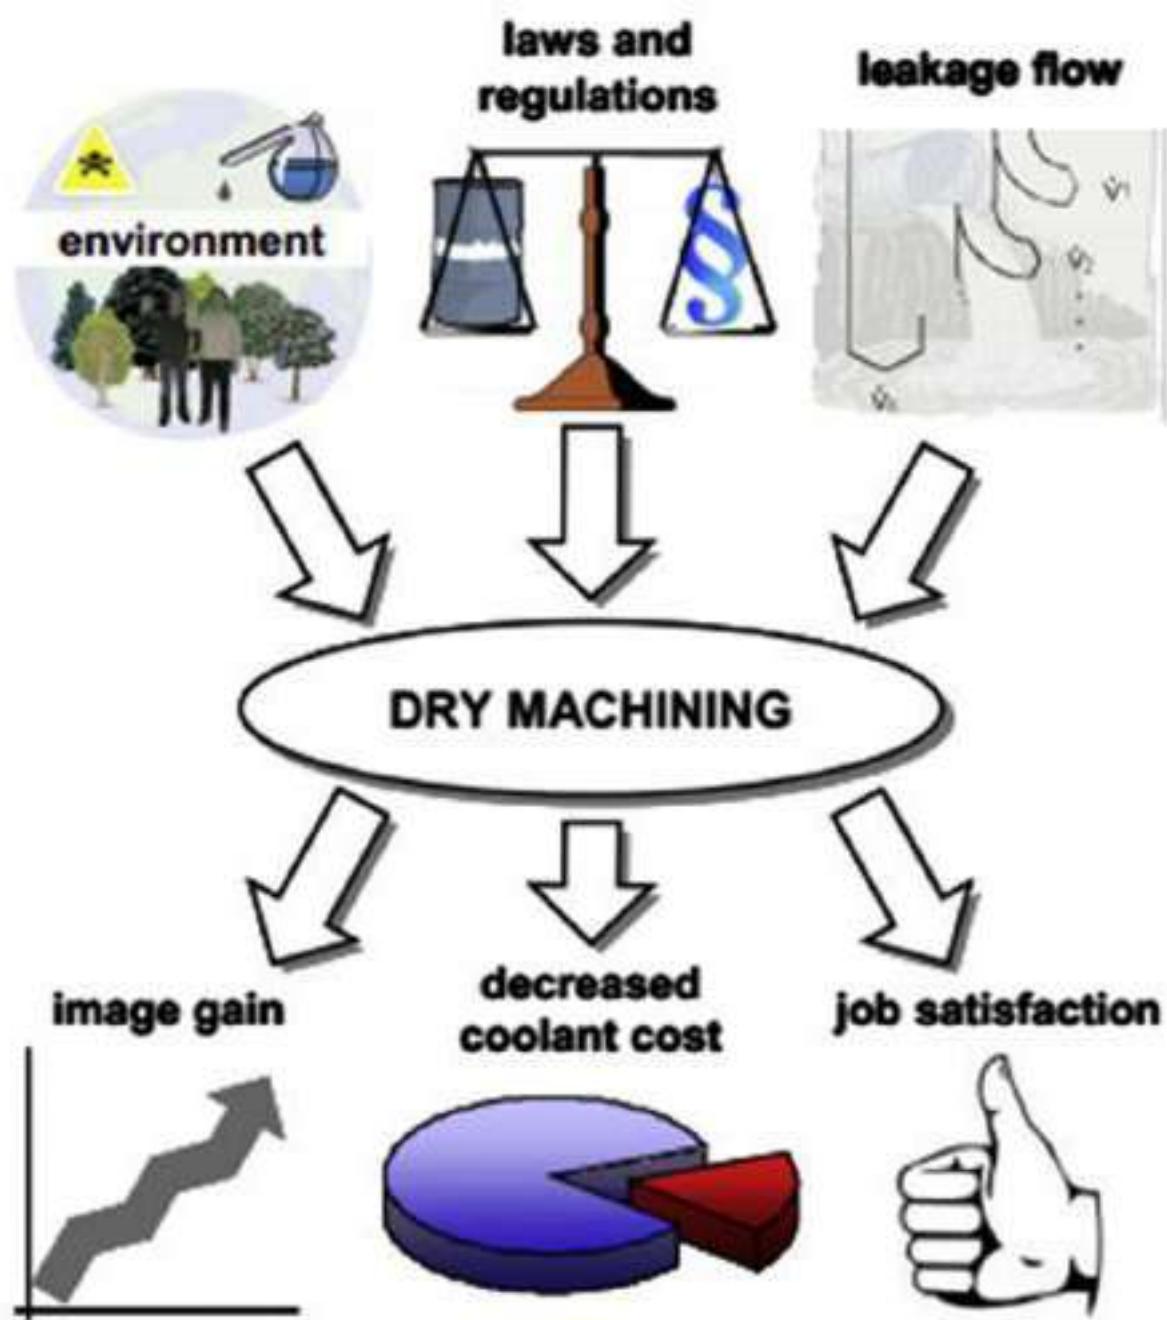

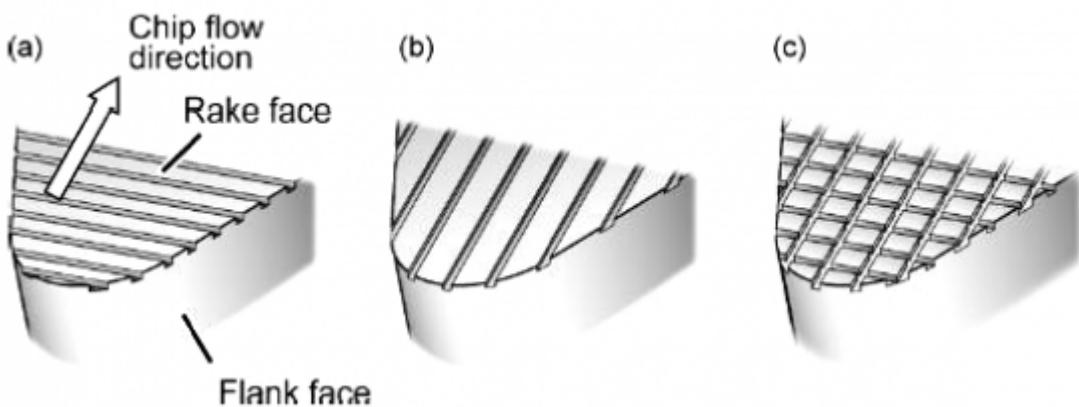

141

Figure 6: 1 .Figure 4 . 1 :

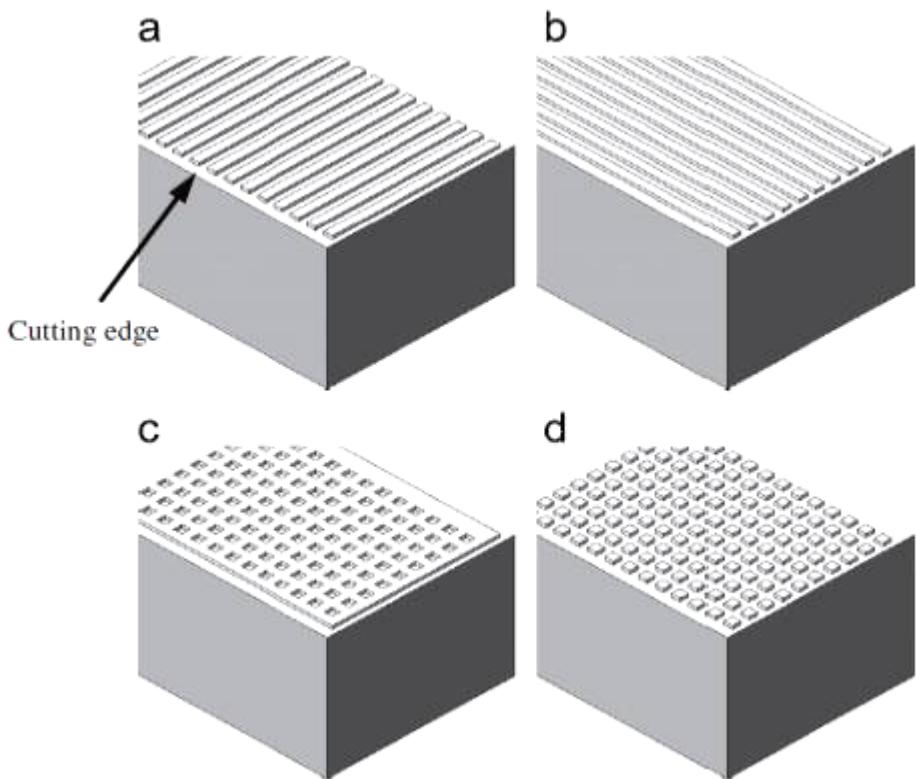

42

Figure 7: Figure 4 . 2 :



43

Figure 8: Figure 4 . 3 :

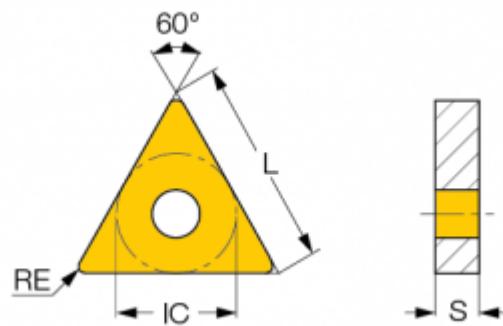


Figure 9: London


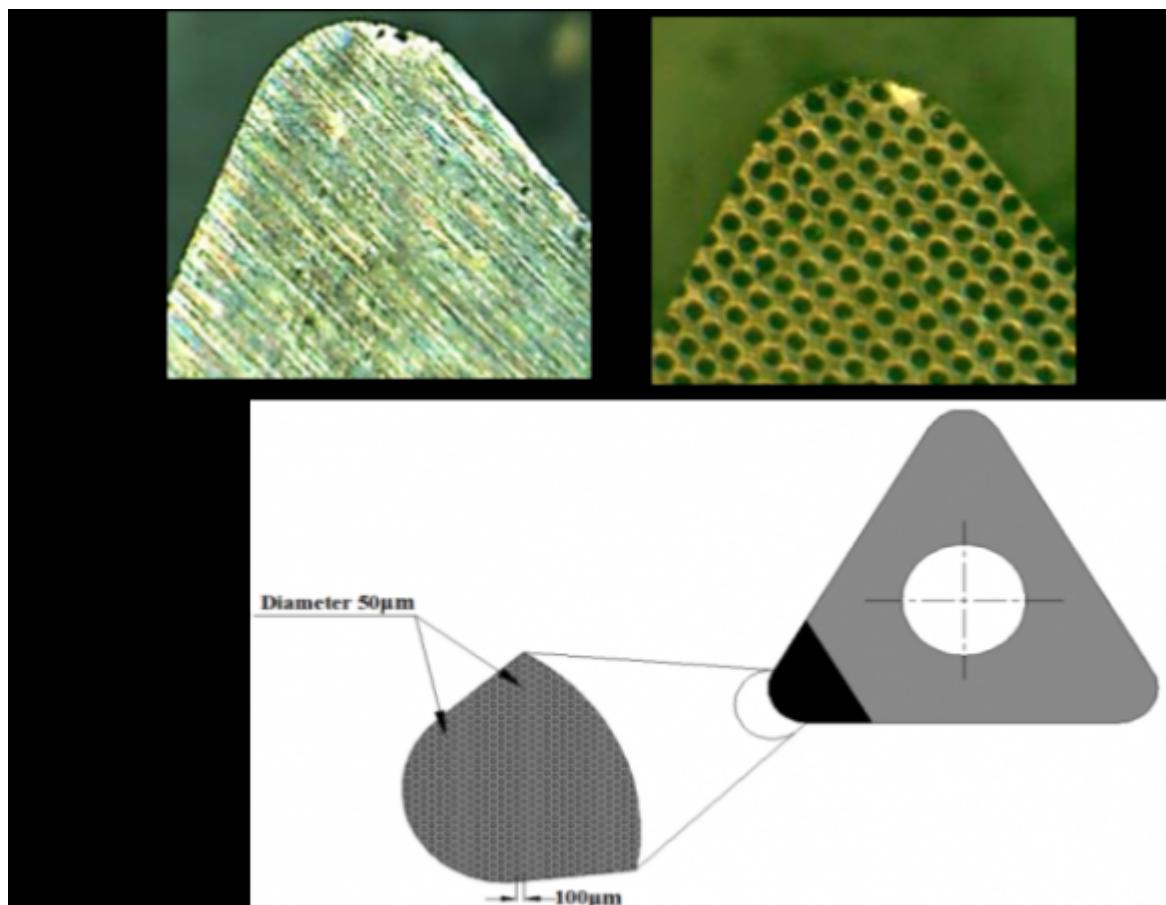


Figure 10: Figure 4 . 4 :
44


Figure STYLEREF 1 \s 3.1 Optical microscope image of (a) Non-textured (NT) tool and textured tool (TT) (b) CAD model textured tool

Figure 10: Figure 4 . 4 :

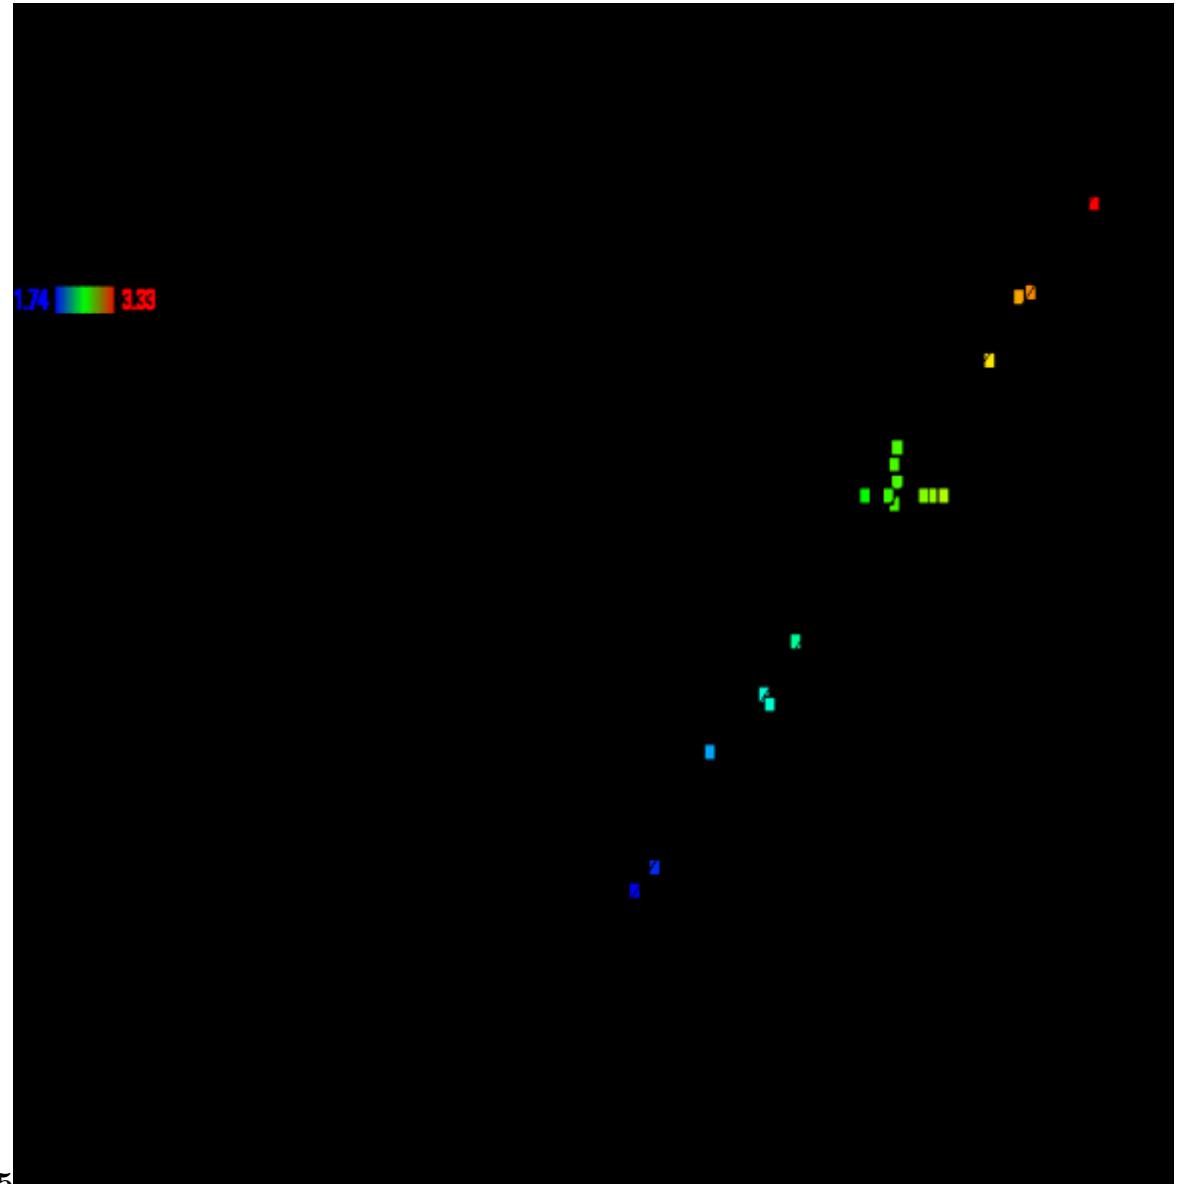


45

Figure 11: Figure 4 . 5 :




46

Figure 12: Figure 4 . 6 :

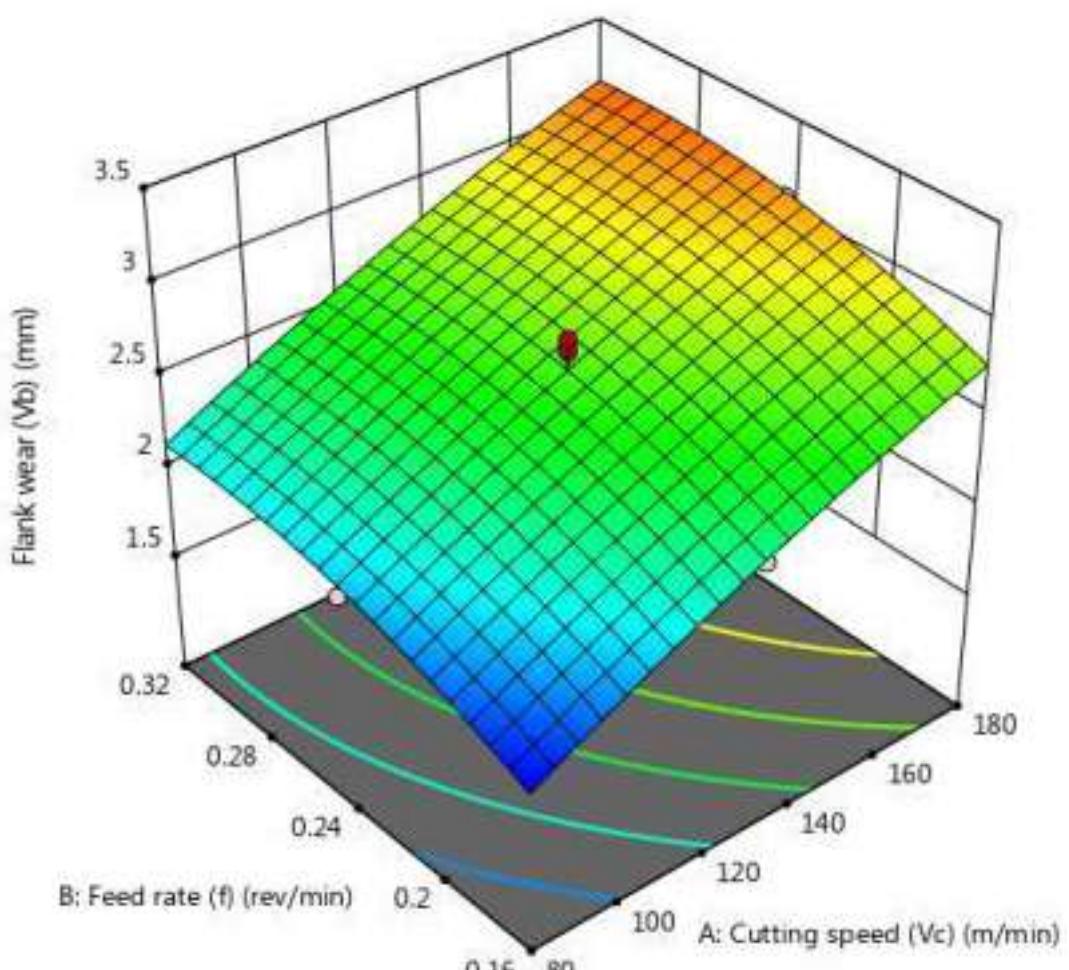

4

Figure 13: Figure 4 .

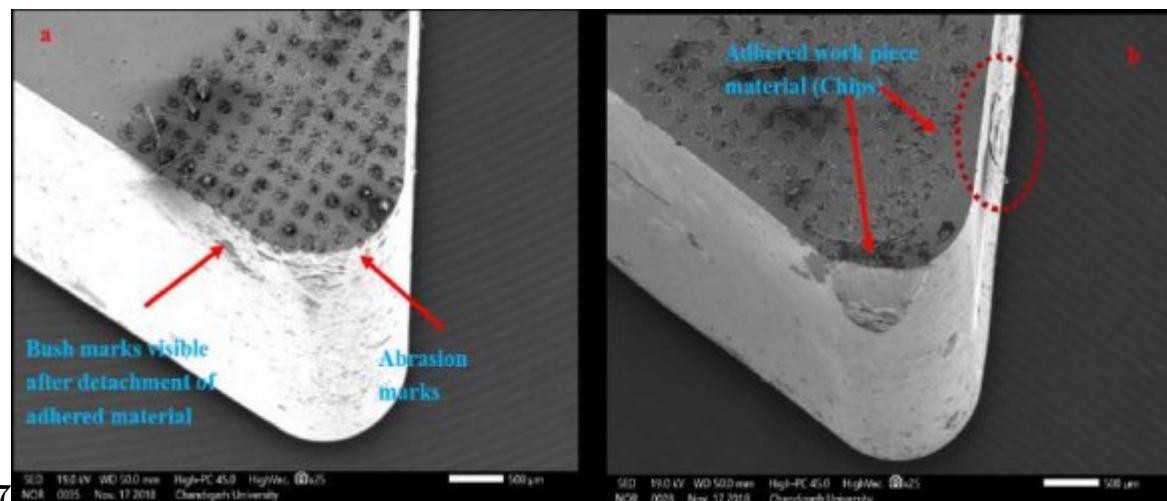

47

Figure 14: Figure 4 . 7 :

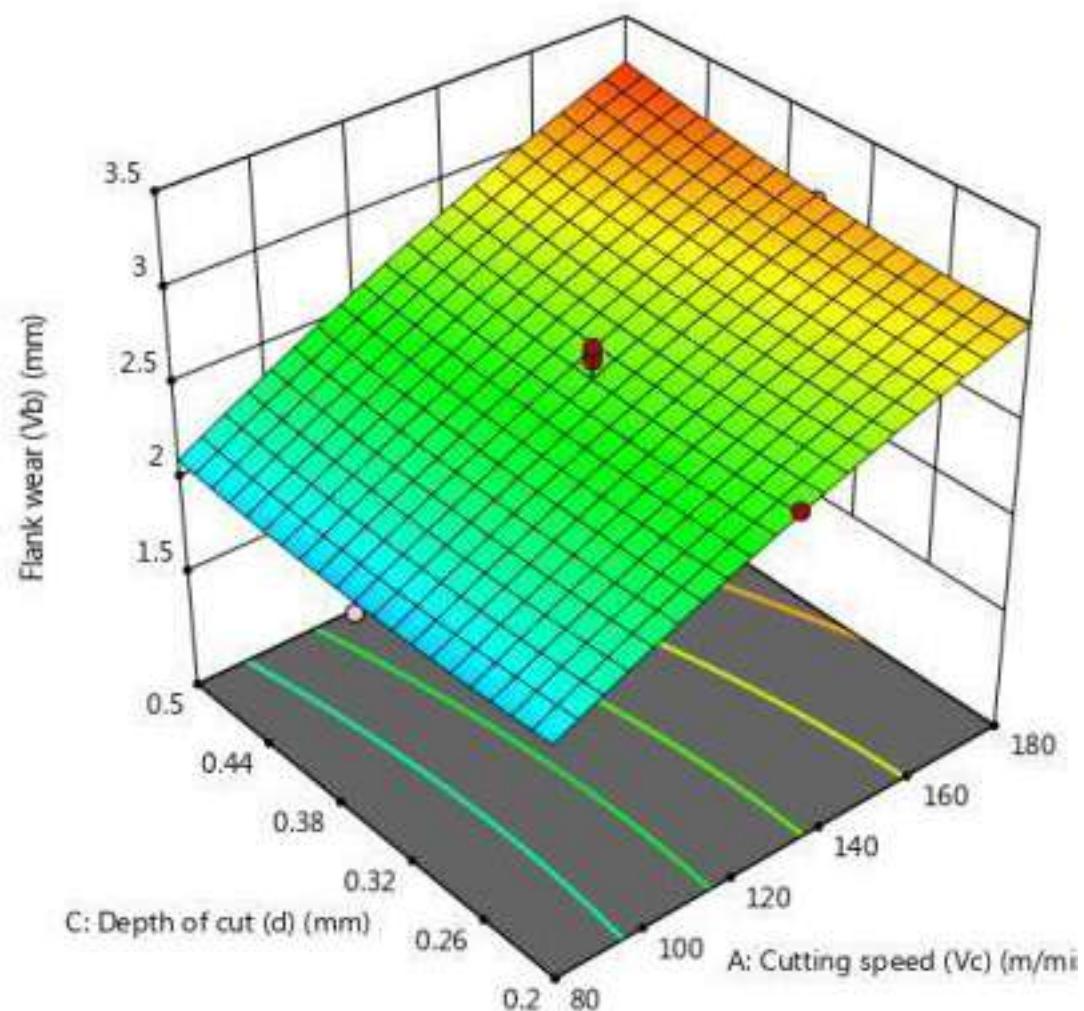


Figure 15:

11

London Journal of Engineering Research

1. Adequate stability at high temperatures
2. Superior thermal shock resistance
3. Superior strength and toughness
4. High hot hardness
5. Excellent resistance to wear

31 Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated Carbide Tool

Figure 16: Table 1 . 1 :

is an environment-friendly method for tribological characteristics improvement.

”Tribology is the study of friction, wear and lubrication of the surfaces in relative motion” (Ian Hutchings, 2017) Lubrication/Cooling capabilities and tribological properties are improved as observed

al., no date). While it may not remove the requirement of grinding, it may relieve the load on costly grinders for the specified application (König, Berktold and Koch, 1993; Chou, Evans and Barash, 2003).

During cutting of metal, there is maximum conversion of energy into heat. Friction inside tool-chip interface and in the workpiece-tool interaction zone generates extra heat at cutting region. The temperature due to friction and plastic deformation at the cutting zone is reached upto 1700°C. During machining 10-20% heat is taken up by tool and rest of 80-90% is transferred to chip (Budak et al., 2010). Heating the tool and workpiece is excessive and also raises their temperature and distortion in the cutting tool

(Motorcu et al., 2016). To overcome these problems of dry machining, sustainable techniques are developed like; a new class of tools, texturing on rake surface of tool, London Journal of Engineering Research Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated Carbide Tool improved tool geometry, and coatings are applied on tools. From all of the above, surface

Figure 17:

31

C	Si	Mn	P	S	Cr	Mo	V
0.33	0.9	0.29	0.03	0.02	5.1	1.2	0.34

Figure 18: Table 3 . 1 :

32

Tensile Strength (MPa)	Yield Strength (MPa)	Young modulus (MPa)	Density (g/cm ³)	Melting Range (°C)	Hardness, Brinell HB	Thermal Conductivity (W/mK)
1590	1380	215 × 10 ³	8.19	1345-1427	195	42.2

3.2 Cutting Tool Material

Cutting tool material selected for the turning tests was uncoated cemented carbide tool; ISO designation -TNMA 160408-THMF (provided by M/s Kennametal India Limited) having specifications shown in Table 3.3. The name of the tool holder was WTJNR1616H16. It was used to rigidly mount the tool mentioned above and had a tool cutting edge angle of 93°.

Figure 19: Table 3 . 2 :

33

Cutting Type insert	Insert Geometry	Insert dimensions (mm)				No. of Edges
		L	IC	R e	S	
TNMA	16.50		9.52	0.80	4.76	6

Figure 20: Table 3 . 3 :

34

Tool Holder	Dimensions (in mm)				LF	LH	HF	WF
	H	B						
WTJNR1616 H16	20	20			125	125	25	25

Figure 21: Table 3 . 4 :

35

Make	RMS Controls, India
Axis	3 axis-X, Y, Z
Sensor	500.0 kgf
Range	0.1 kgf
Resolution	0.05 % Full scale
Accuracy	0.05 %
Linearity	Front side push button switch
Zero/Tare	230 V AC
Power supply	Table
Model	Top

Figure 22: Table 3 . 5 :

36

Make	JEOL, Japan
Model	JSM-6510LV
Maximum magnification	5X to 300,000X
Resolution	3 nm
Operating voltage	0.5 KV to 30 KV
Maximum specimen	150 mm diameter
Objective lens	Super conical

Figure 23: Table 3 . 6 :

41

Exp. No	Cutting speed: Vc (m/min.)	Feed rate: f (mm/rev)	Depth of cut: d (mm)	Flank VB	Surface
					wear: Ra (μ m)
1	130	0.24	0.35	2.81	1.84
2	180	0.16	0.2	2.65	1.78
3	180	0.32	0.2	3.11	2.12
4	80	0.16	0.2	1.74	1.86
5	80	0.32	0.2	2.19	2.6
6	80	0.16	0.5	1.81	2.23
7	80	0.24	0.35	2	2.34
8	80	0.32	0.5	2.21	2.98
9	130	0.24	0.35	2.54	2.02
10	130	0.24	0.5	2.65	2.21
11	130	0.24	0.35	2.77	1.99
12	130	0.24	0.35	2.54	2.18
13	130	0.24	0.2	2.64	1.87
14	130	0.32	0.35	2.64	2.24
15	180	0.16	0.5	2.97	2.04
16	130	0.24	0.35	2.74	1.94
17	180	0.24	0.35	3.07	2.18
18	130	0.16	0.35	2.3	1.78
19	130	0.24	0.35	2.62	1.96
20	180	0.32	0.5	3.33	2.44

Figure 24: Table 4 . 1 :

42

Source models	R 2	PRESS values	Remarks
Linear	0.9281	0.3621	
2FI	0.9364	0.6941	
Quadratic	0.9707	0.2568	Suggested
Cubic	0.9743	19.70	Aliased

Figure 25: Table 4 . 2 :

43

Source models	R 2	PRESS values	Remarks
Linear	0.7169	0.8139	
2FI	0.7610	2.06	
Quadratic	0.9099	0.2107	Suggested
Cubic	0.9613	3.27	Aliased

4.1 ANOVA Analysis

The ANOVA test was used to determine the statistical significance of models and input variables produced by RSM. Findings through ANOVA for VB and Ra models are shown in Table 4.4 and Table 4.6 respectively. The importance of RSM models and input variables may be determined by examining their associated p-value (Prob>F). If the p-value < 0.05 (Prob>F, at 95% confidence level), the contribution of parameters is considered significant. Using the ANOVA test, it

was determined that models for VB and Ra are fitted and significant statistically. ANOVA findings indicate that A, B, C, AB, AC, BC, A^2 , B^2 , and C^2 , are all statistically significant variables for both output responses. Lack of fit: F-test was used to determine how well the generated response models fit the input data. F-values (i.e., the ratio between mean square lack of fit and pure error mean square) for lack of fit test were found as 0.3969, and 0.2749 for VB and Ra models, respectively and their associated p-values (>0.05)

Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated Carbide Tool

Figure 26: Table 4 . 3 :

44

Source	Sum of *	DF	Mean	F value	p-value	Remarks
Model	Squares 3.27	9	0.3635	36.76	< 0.0001	Prob>F significant
A-Cutting speed (Vc)	2.68	1	2.68	271.31	< 0.0001	
B-Feed rate (f)	0.404	1	0.404	40.85	< 0.0001	
C-Depth of cut (d)	0.041	1	0.041	4.14	0.0692	
AB	0.0001	1	0.0001	0.0114	0.9172	
AC	0.0253	1	0.0253	2.56	0.1407	
BC	0.0028	1	0.0028	0.2844	0.6055	
A^2	0.0118	1	0.0118	1.19	0.3007	
B^2	0.0468	1	0.0468	4.73	0.0547	
C^2	0.0055	1	0.0055	0.5517	0.4747	
Residual	0.0989	10	0.0099			
Lack of Fit	0.0281	5	0.0056	0.3969	0.8333	not significant
Pure Error	0.0708	5	0.0142			
Cor Total	3.37	19				

*Degrees of Freedom

Figure 27: Table 4 . 4 :

45

Std. Deviation	0.0994	R 2	0.9707
Mean	2.57	Adjusted R 2	0.9443
C.V. %	3.87	Predicted R 2	0.9238
PRESS	0.2568	Adeq Precision	22.2693

Table 4.6: ANOVA Results for Surface Roughness (Ra)

Source	Sum of *	DF	Mean	F value	p-value	Remarks
Model	Squares 1.61142	9	0.179	22.332	0.00002	Prob>F significant
A-Cutting speed (Vc)	0.21025	1	0.210	26.224	0.00045	
B-Feed rate (f)	0.72361	1	0.724	90.253	0.00000	
C-Depth of cut (d)	0.27889	1	0.279	34.785	0.00015	

Figure 28: Table 4 . 5 :

47

Std. Deviation	0.0895	R 2	0.9526
Mean	2.13	Adjusted R 2	0.9099
C.V. %	4.20	Predicted R 2	0.8755
PRESS	0.2107	Adeq Precision	19.6007

Figure 29: Table 4 . 7 :

48

Response		Empirical Model Equations (In Terms of Actual Factors)			
Sr.	No.	Factors	Factors)	Factors)	Factors)
1	VB	$-0.650240 + 0.014767 * Vc + 12.96534 * f - 1.55919 * d - 0.000938 * Vc * f + 0.007500 * Vc * d - 1.56250 * f * d - 0.000026 * (Vc)^2$	-	+	$20.38352.97980 * (f) * (d)^2$
2	Ra	$2.09936 - 0.021622 * Vc + 6.63144 * f + 0.571313 * d - 0.023438 * Vc * f - 0.002833 * Vc * d + 0.729167 * f * d + 0.000097 * (Vc)^2$	-	+	$0.994318 1.05051 * (f)^2 * (d)^2$

Figure 30: Table 4 . 8 :

49

Constraints	Goal	Lower Limit	Upper Limit
Cutting Speed (m/min.)	is in range	80	180
Feed rate (mm/rev.)	is in range	0.16	0.32
Depth of cut (mm)	is in range	0.2	0.5
Flank wear, VB (µm)	minimize	1.74	3.33
Surface roughness, Ra (µm)	minimize	1.78	2.98

Figure 31: Table 4 . 9 :

S No.	1	2	3	4	5	Cutting Speed (m/min.)	Feed rate (mm/revolution)	Solutions (mm)	Depth of cut (mm)	VB (µm)	Optimization	London Jour-
	86.616	0.160				86.616	0.160	Ra (µm)			Desirabil-	of
	87.054	0.160				87.054	0.160	ity	Remarks	0.200	En-	gi-
	87.573	0.160				87.573	0.160	1.820	1.799	0.967	Se-	neer-
	85.628	0.160				85.628	0.160	lected	0.200	1.824	ing	Re-
	88.012	0.160				88.012	0.160	1.795	0.967	0.200	Re-	search
								1.830	1.790	0.967		
								0.200	1.808	1.808		
								0.967	0.200	1.835		
								1.787	0.967			

4.4 Confirmation Tests

Confirmation tests (replicated thrice) have been carried out under the same experimental settings and tooling circumstances, with suggested optimal levels of machining variables. Table 4.11 demonstrates the error between the expected response and the experimental results from validating the precision of the mathematical model created for both VB and Ra during the confirmatory tests within the 95% prediction range, illustrated in Table 4.11.

23 Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated Carbide Tool 45 4.3 Multi-Response Optimization of Turning Parameters || Volume 23 Issue 2 ?”? Compilation 1.0 © 2023 Great Britain Journals Press

Figure 32: Table 4 .

	RSM	Experimentally	Error
	Predicted	observed value	(%)
Tool flank wear (μm)	1.82	1.89	3.84%
Surface roughness (μm)	1.79	1.87	4.47%

V. CONCLUSION

Optimization of Turning Parameters using RSM During Turning of AISI H11 with Dimple Textured Uncoated Carbide Tool

Figure 33: Table 4 .

191 [| ()] , | , © . 1.0. 2023. Britain Journals Press. 23.

192 [Pavel] (no date) 'Surface Quality and Tool Wear in Interrupted Hard Turning of 1137 Steel Shafts, R Pavel .

193 [Dudzinski ()] 'A review of developments towards dry and high speed machining of Inconel 718 alloy'. D Dudzinski . 10.1016/S0890-6955(03)00159-7. [https://doi.org/10.1016/S0890-6955\(03\)00159-7](https://doi.org/10.1016/S0890-6955(03)00159-7) International Journal of Machine Tools and Manufacture 2004. 44 (4) p. .

196 [Sharma et al. ()] 'Advances in the turning process for productivity improvement-A review'. V S Sharma , M Dogra , N M Suri . 10.1243/09544054JEM1199. <https://doi.org/10.1243/09544054JEM1199> Proceedings of the Institution of Mechanical Engineers 2008. 222 (11) p. . (Part B: Journal of Engineering Manufacture)

200 [Motorcu ()] 'Analysis of the cutting temperature and surface roughness during the orthogonal machining of AISI 4140 alloy steel via the taguchi method'. A R Motorcu . 10.17222/mit.2015.021. <https://doi.org/10.17222/mit.2015.021> Materiali in Tehnologije 2016. 50 (3) p. .

203 [Ghosh and Rao ()] 'Application of sustainable techniques in metal cutting for enhanced machinability : a review'. S Ghosh , P V Rao . 10.1016/j.jclepro.2015.03.039. <https://doi.org/10.1016/j.jclepro.2015.03.039> Journal of Cleaner Production 2015. (Preprint). Available at)

206 [Fatima and Mativenga ()] 'Assessment of tool rake surface structure geometry for enhanced contact phenomena'. A Fatima , P T Mativenga . 10.1007/s00170-013-5079-6. <https://doi.org/10.1007/s00170-013-5079-6> International Journal of Advanced Manufacturing Technology 2013. 69 (1-4) p. .

209 [Chao and Trigger ()] 'Controlled Contact Cutting Tools'. B T Chao , K J Trigger . 10.1115/1.40082. <https://doi.org/10.1115/1.40082> Journal of Engineering for Industry 1959. 81 (2) p. .

211 [Sharma et al. ()] 'Cooling techniques for improved productivity in turning'. V S Sharma , M Dogra , N M Suri . 10.1016/j.ijmachtools.2008.12.010. <https://doi.org/10.1016/j.ijmachtools.2008.12.010> International Journal of Machine Tools and Manufacture 2009. 49 (6) p. .

214 [Kawasegi ()] Development of cutting tools with microscale and nanoscale textures to improve frictional behavior, N Kawasegi . 10.1016/j.precisioneng.2008.07.005. <https://doi.org/10.1016/j.precisioneng.2008.07.005> 2009. (Precision Engineering. Preprint)

217 [Klocke and Eisenblätter ()] 'Dry Cutting'. F Klocke , G Eisenblätter . CIRP Annuals 1997. 46 (2) p. .

218 [Sreejith and Ngoy ()] 'Dry machining: Machining of the future'. P S Sreejith , B K A Ngoy . 1016/S0924-0136(00)00445-3. [https://doi.org/10.1016/S0924-0136\(00\)00445-3](https://doi.org/10.1016/S0924-0136(00)00445-3) Journal of Materials Processing Technology 2000. 101 (1) p. .

220 [Wakuda ()] 'Effect of surface texturing on friction reduction between ceramic and steel materials under lubricated sliding contact'. M Wakuda . 10.1016/S0043-1648. <https://doi.org/10.1016/S0043-1648> Wear 2003. 254 (3-4) p. .

223 [Costa and Hutchings ()] 'Effects of die surface patterning on lubrication in strip drawing'. H L Costa , I M Hutchings . 10.1016/j.jmatprotec.2008.03.026. <https://doi.org/10.1016/j.jmatprotec.2008.03.026> Journal of Materials Processing Technology 2009. 209 (3) p. .

226 [Debnath et al. ()] 'Environmental friendly cutting fluids and cooling techniques in machining: A review'. S Debnath , M M Reddy , Q S Yi . 10.1016/j.jclepro.2014.07.071. <https://doi.org/10.1016/j.jclepro.2014.07.071> Journal of Cleaner Production 2014. 83 p. .

229 [Shokrani et al. ()] 'Environmentally conscious machining of difficult-to-machine materials with regard to cutting fluids'. A Shokrani , V Dhokia , S T Newman . 10.1016/j.ijmachtools.2012.02.002. <https://doi.org/10.1016/j.ijmachtools.2012.02.002> International Journal of Machine Tools and Manufacture 2012. 57 p. .

233 [Kundrák ()] 'Environmentally friendly precision machining'. J Kundrák . 10.1080/AMP-200060612. <https://doi.org/10.1080/AMP-200060612> Materials and Manufacturing Processes 2006. 21 (1) p. .

235 [Chou et al. ()] 'Experimental investigation on cubic boron nitride turning of hardened AISI 52100 steel'. Y K Chou , C J Evans , M M Barash . 10.1016/S0924-0136(02)000. [https://doi.org/10.1016/S0924-0136\(02\)000](https://doi.org/10.1016/S0924-0136(02)000) Journal of Materials Processing Technology 2003. 134 (1) p. .

238 [Kim ()] 'Finite element modeling of hard turning process via a micro-textured tool'. D M Kim . 10.1007/s00170-014-6747-x. <https://doi.org/10.1007/s00170-014-6747-x> The International Journal of Advanced Manufacturing Technology 2015. 78 (9-12) p. .

241 [Pettersson and Jacobson ()] 'Friction and wear properties of micro textured DLC coated surfaces in boundary lubricated sliding'. U Pettersson , S Jacobson . 10.1023/B:TRIL.0000044504.76164.4e. <https://doi.org/10.1023/B:TRIL.0000044504.76164.4e> Tribology Letters 2004. 17 (3) p. .

244 [Soroka ()] Hard Turning and the Machine Tool, D P Soroka . 2003. p. .

245 [Costa and Hutchings ()] 'Hydrodynamic lubrication of textured steel surfaces under reciprocating sliding conditions'. H L Costa , I M Hutchings . 10.1016/j.triboint.2007.01.014. <https://doi.org/10.1016/j.triboint.2007.01.014> Tribology International 2007. 40 (8) p. .

248 [Enomotoa and Sugihara ()] 'Improvement of anti-adhesive properties of cutting tool by nano/micro textures and
249 its mechanism'. T Enomotoa , T Sugihara . 10.1016/j.proeng.2011.11.086. <https://doi.org/10.1016/j.proeng.2011.11.086> *Procedia Engineering* 2011. 19 p. .

251 [Enomoto and Sugihara ()] 'Improving anti-adhesive properties of cutting tool surfaces by nano-/micro-textures'.
252 T Enomoto , T Sugihara . 10.1016/j.cirp.2010.03.130. <https://doi.org/10.1016/j.cirp.2010.03.130> *CIRP Annals -Manufacturing Technology* 2010. 59 (1) p. .

254 [Pettersson and Jacobson ()] 'Influence of surface texture on boundary lubricated sliding contacts'. U Pettersson ,
255 S Jacobson . 10.1016/S0301-679X(03)00104-X. [https://doi.org/10.1016/S0301-679X\(03\)00104-X](https://doi.org/10.1016/S0301-679X(03)00104-X)
256 *Tribology International* 2003. 36 (11) p. .

257 [Chang ()] 'Investigation of microstructured milling tool for deferring tool wear'. W Chang .
258 10.1016/j.wear.2010.12.026. <https://doi.org/10.1016/j.wear.2010.12.026> *Wear* 2011. 271
259 (9-10) p. .

260 [Zhan and Yang ()] 'Investigation on Dimples Distribution Angle in Laser Texturing of Cylinder-Piston Ring
261 System'. J Zhan , M Yang . 10.1080/10402004.2012.694581. <https://doi.org/10.1080/10402004.2012.694581> *Tribology Transactions* 2012. 55 (5) p. .

263 [Blatter ()] 'Lubricated sliding performance of laser-patterned sapphire'. A Blatter . 10.1016/S0043-1648(99)0015.
264 [https://doi.org/10.1016/S0043-1648\(99\)0015](https://doi.org/10.1016/S0043-1648(99)0015) *Wear* 1999. 232 (2) p. .

265 [Xie ()] 'Micro-grinding of micro-groove array on tool rake surface for dry cutting of titanium alloy'. J Xie .
266 10.1007/s12541-012-0242-9. <https://doi.org/10.1007/s12541-012-0242-9> *International Journal of
267 Precision Engineering and Manufacturing* 2012. 13 (10) p. .

268 [Jianxin ()] 'Performance of carbide tools with textured rake-face filled with solid lubricants in dry cutting
269 processes'. D Jianxin . 10.1016/j.ijrmhm.2011.08.002. <https://doi.org/10.1016/j.ijrmhm.2011.08.002> *International Journal of Refractory Metals and Hard Materials* 2012. 30 (1) p. .

271 [Sharma and Pandey ()] 'Recent advances in turning with textured cutting tools: A review'. V Sharma , P M
272 Pandey . 10.1016/j.jclepro.2016.07.138. <https://doi.org/10.1016/j.jclepro.2016.07.138> *Journal
273 of Cleaner Production* 2016. 137 p. .

274 [Tseng ()] 'Recent developments in micromilling using focused ion beam technology'. A A Tseng . 10.1088/0960-
275 1317/14/4/R01. <https://doi.org/10.1088/0960-1317/14/4/R01> *Journal of Micromechanics and Microengi-
276 neering* 2004. 14 (4) . (Available at: [htt ps:](http://htt.ps))

277 [Etsion ()] 'State of the art in laser surface texturing'. I Etsion . 10.1115/1.1828070. <https://doi.org/10.1115/1.1828070> *Journal of Tribology* 2005. 127 (1) p. .

279 [Mosoarof ()] 'Surface Texture Manufacturing Techniques and Tribological Effect of Surface Texturing on Cutting
280 Tool Performance: A Review'. M H Mosoarof . 10.1080/10408436.2016.1186597. <https://doi.org/10.1080/10408436.2016.1186597> *Critical Reviews in Solid State and Materials Sciences* 2016. 41 (6) p. .

282 [Ling ()] 'Surface texturing of drill bits for adhesion reduction and tool life enhancement'. T D Ling . 10
283 07/s11249-013-0198-7. <https://doi.org/10.1088/0960-1317/14/4/R01> *Tribology Letters* 2013. 52 (1) p. .

284 [Kovalchenko ()] 'The effect of laser surface texturing on transitions in lubrication regimes during unidirec-
285 tional sliding contact'. A Kovalchenko . 10.1016/j.triboint.2004.08.004. <https://doi.org/10.1016/j.triboint.2004.08.004> *Tribology International* 2005. 38 (3) p. .

287 [Zhang et al. ()] 'Tool life and cutting forces in end milling Inconel 718 under dry and minimum quantity', S
288 Zhang , J F Li , Y W Wang . 2012.

289 [Hutchings (ed.) ()] *Tribology: Friction and Wear of Engineering Materials*, Ian Hutchings , PS . Butterworth-
290 Heinemann (ed.) 2017.

291 [König et al. ()] 'Turning versus Grinding -A Comparison of Surface Integrity Aspects and Attainable Accu-
292 rancies'. W König , A Berktold , K F Koch . 10.1016/S0007-8506(07)623. [https://doi.org/10.1016/S0007-8506\(07\)623](https://doi.org/10.1016/S0007-8506(07)623) *CIRP Annals -Manufacturing Technology* 1993. 42 (1) p. .